

A Review on Antibacterial Activity of Nanoparticles

Badr-Edine Sadoq ¹, Mohammed Reda Britel ¹, Adel Bouajaj ¹, Ramzi Maâlej ², Ahmed Touhami ³, Marwa Abid ⁴, Hanen Douiri ⁵, Fakhita Touhami ¹, Amal Maurady ^{1,6,*}

¹ Laboratory of innovative technologies, National School of Applied Sciences of Tangier, Abdelmalek Essaadi University, Tetouan, Morocco

² Georesources Materials Environment and Global Changes Laboratory (GEOGLOB), Faculty of Sciences of Sfax, University of Sfax, Tunisia

³ Department of Physics and Astronomy, University of Texas Rio Grande Valley Edinburg, United States

⁴ Department of Chemistry, University of Sfax, Sfax, Tunisia

⁵ Department of physic, University of Sfax, Sfax, Tunisia

⁶ Faculty of Sciences and Techniques of Tangier, Abdelmalek Essaadi University, Tetouan, Morocco

* Correspondence: amal.maurady.ma@gmail.com (A.M.);

Scopus Author ID 36011971000

Received: 24.08.2022; Accepted: 20.09.2022; Published: 17.11.2022

Abstract: The increasing resistance of bacteria to antibiotic agents is a main global public health problem. The use of nanoparticles is one of the promising ways to overcome microbial resistance to antimicrobial agents. Metal nanoparticles are increasingly used to target bacterial strains. Advances in nanotechnology, in particular the ability to synthesize nanoparticles of specific size and shape, are likely to lead to the development of new antibacterial agents. The antibacterial activities of nanoparticles are largely influenced by their sizes and large surface area/mass ratio. The antibacterial mechanisms of nanoparticles are poorly understood, but the currently accepted mechanisms include oxidative stress induction, metal ion release, and non-oxidative mechanisms. In this review, we have focused on the antibacterial activity of nanoparticles and their main mechanisms of action against bacteria. We also discuss the recent therapeutic strategies to control bacterial virulence and biofilm formation by targeting quorum sensing in bacteria without impeding bacterial growth. On the other hand, we reviewed five widely used databases of nanoparticles, aiming to provide the nanoscience community with valuable information about the specific content and function of these databases.

Keywords: nanoparticles; metal nanoparticles; antibacterial activity; antibacterial mechanisms; antimicrobial resistance; anti-quorum sensing; database.

© 2022 by the authors. This article is an open-access article distributed under the terms and conditions of the Creative Commons Attribution (CC BY) license (<https://creativecommons.org/licenses/by/4.0/>).

1. Introduction

Bacterial infections remain one of the leading causes of morbidity and mortality worldwide. According to the report published by the World Health Organization, bacterial resistance to antimicrobial agents is a major global public health problem [1]. The absence of new effective antimicrobial agents is mainly associated with increased bacterial resistance. This has sparked initiatives worldwide to develop more effective antimicrobial compounds to address the problem of antimicrobial resistance [2–4].

The scientific community is highly concerned, and researchers are probing every possible way to overcome the antimicrobial resistance problem. One promising and important pathway is using nanoparticles to treat bacterial infections. Innovative advances in nanotechnology, in particular, the development of technology and techniques for synthesizing

NPs with specific characteristics, are likely to develop new nano-antimicrobials involving quorum sensing nano-inhibitors. In addition to their high surface/volume ratio [5,6], nanoparticles have specific physical, chemical, structural, mechanical, electrical, and optical properties that make them effective and promising antibacterial agents [7]. Furthermore, their ability to interact with the bacterial cell barrier, inhibition of bacterial protein and DNA synthesis, and the regulation of bacterial metabolic processes are important properties that attract scientists to this area of research and development [8].

Several types of NPs are currently used as antimicrobial agents. For example, silver (Ag), zinc oxide (ZnO), and titanium oxide (TiO₂) nanoparticles [9–13] show significant antimicrobial activities against several microorganisms [14–18]. As shown in Figure 1, a continuous increase in publications was observed, especially in the last few years. Silver nanoparticles got more importance for investigating applications as antimicrobial agents, primarily focusing on bacteria.

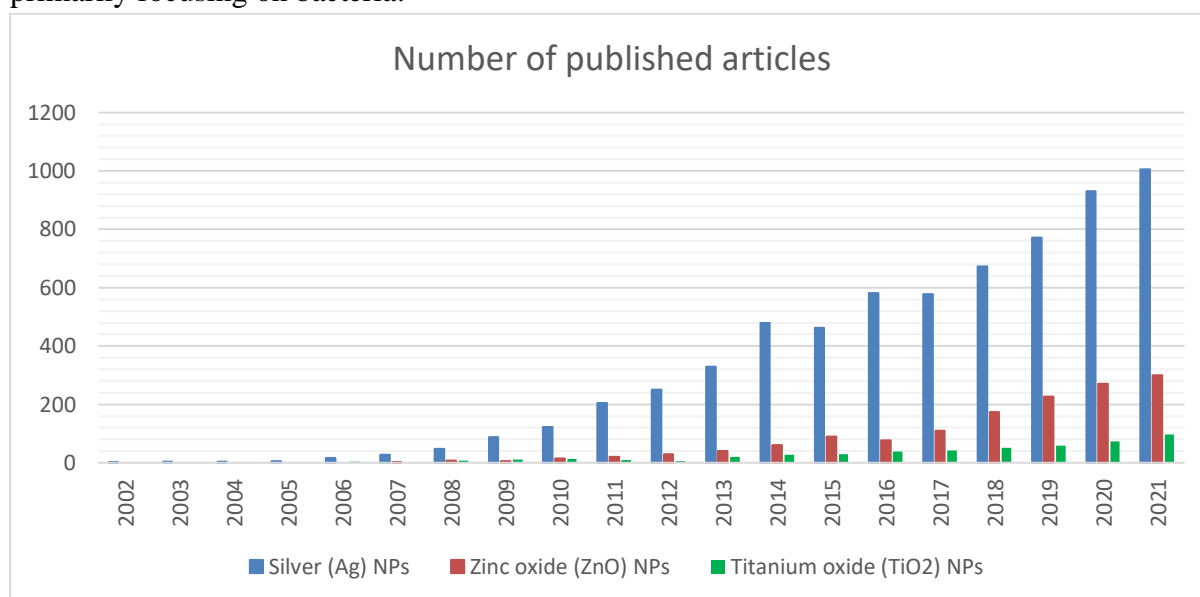


Figure 1. The number of published research articles on the antimicrobial activity of silver (Ag), zinc oxide (ZnO), and titanium oxide (TiO₂) nanoparticles. SCOPUS database was used, and antimicrobial activity of silver, zinc oxide, and titanium oxide were used as keywords.

The detailed antibacterial mechanisms of nanoparticles have not been fully explained. It is generally described as adhering to one of three models: formation of reactive oxidizing species (ROS) [19], metal ion release [20], and non-oxidative mechanisms [21]. It is also suggested that these three types of mechanisms can occur simultaneously. Another mechanism through which metal and metal oxide nanoparticles reduce the formation of biofilms and virulence of bacteria is the interruption in quorum sensing (QS), a bacterial gene expression system regulated by small signaling molecules [22–26].

Many reviews about NPs synthesis, types, and antimicrobial activities are reported exhaustively elsewhere [27–33]. Hence, this review intends to provide a valuable reference for researchers interested in using nanoparticles to develop nano-antimicrobials. In this review, we discuss the synthesis of nanoparticles, including chemical, physical and biological synthesis methods. We also discuss the methods for the characterization of nanoparticles. More importantly, we discuss the biological applications of metal and metal oxide NPs, such as silver (Ag) NPs, zinc oxide (ZnO) NPs, and titanium dioxides (TiO₂) NPs, focusing on antibacterial mechanisms and anti-quorum sensing properties. Finally, we discuss the widely used databases to process the information on nanoparticle structure and physicochemical characteristics.

Understanding the function and available data in these databases is needed for scientists to retrieve specific information for research on nanomaterials.

2. Bacteria Resistance

2.1. Antibiotic resistance.

Antibiotic resistance is the most difficult medical challenge in treating infectious diseases. In the first few uses of antibiotics, resistance issues were marginal. However, the overuse of antibiotics has made it possible to select resistant organisms that colonize and induce difficult-to-treat infections. When bacteria become resistant to several types of antibiotics, called multidrug-resistant (MDR), treating these kinds of infections is extremely difficult [34,35].

Three groups of antibiotic-resistant pathogens emerge as major health problems [34]. The first group contains the methicillin-resistant strain *Staphylococcus aureus* (MRSA), which causes 19,000 deaths per year in the USA [36]. The cell membrane of this Gram-positive bacteria is mainly composed of a thick layer of peptidoglycan macromolecule (the main target of antibiotics), the periplasmic space, and the plasma membrane.

The second group of pathogens includes multidrug-resistant Gram-negative bacteria (MDR), which are less common than MRSA but present a serious threat to the onset of incurable diseases [34]. These different strains are resistant to some or all types of antibiotics commonly used to treat Gram-negative bacterial infections. The search for new effective antibiotics is made difficult because gram-negative bacteria can block all entry of antibiotics. If certain antibiotics manage to cross this barrier, the efflux pumps expel them [37]. On the other hand, Gram-negative bacteria have a different membrane from Gram-positive bacteria. Their membrane comprises an outer membrane, a thin layer of peptidoglycan, the periplasmic space, and a plasma membrane.

The third group of resistant pathogens contains other MDRs in addition to the ultra-resistant *Mycobacterium tuberculosis* strain (XRD-TB or MDR-TB), one of the greatest threats in developing countries. Treatment for MDR-TB requires two years of antibiotics, accompanied by serious side effects. XRD-TB is more difficult to treat and often fatal [37].

2.2. Bacterial resistance to nanoparticles.

In contrast to traditional antibiotics, nanoparticles can overcome existing antibiotic resistance mechanisms. NPs have characteristic dimensions <100 nm. The physical and chemical properties of nanoparticles, such as morphology and size, which range from 1 to 100 nm, are the main reasons NPs can effectively overcome microbial resistance and be considered an alternative to antibiotics [38,39]. The smaller the size and spherical the NPs are, the greater the surface-volume ratio is achieved, which helps to enhance the nanoparticles' antimicrobial activities [40].

3. Antibacterial Nanoparticles

With the problems of resistance to antimicrobial agents, nanoparticles have become a promising strategy for destroying bacteria. Nanoparticles (NPs) are defined as particles having a size of the nanometric scale (between 1 and 100nm) [41–43]. The application of nanomaterials as new antimicrobials could provide modes of action and different cellular

targets compared to conventional antibiotics. NPs can be organic or inorganic; however, inorganic NPs are the most widely used due to their ability to withstand adverse reaction conditions [44]. Several types of NPs, including nanoparticles of metals and metal oxides, have been developed and evaluated by different researchers; examples include silver (Ag), zinc oxide (ZnO), and titanium dioxide (TiO₂). Nanoparticles act on bacteria by several different methods, and the mode of action of these NPs varies with each different type (Table 1).

Table 1. Mode of action of various nanoparticles against pathogenic microbes.

Type of NPS	Mode of action	Bacterial strains	References
Silver (Ag)	- Inhibition of DNA replication and the respiratory chain in bacteria and fungi. - Creation of reactive oxygen species. - Inhibit the formation of the cell wall of gram-positive bacteria.	- <i>S.aureus</i> - <i>P.aeruginosa</i> - <i>E.coli</i>	[45,46]
Zinc oxide (ZnO)	- Hydrogen peroxide generated on the surface of the ZnO penetrates into bacterial cells and disrupts their metabolism. - Zn ²⁺ ions released during the dissolution of the nanoparticles damage the cell membrane and interact with intracellular components. - Formation of reactive oxygen species. - Disruption to the bacterial cell membrane.	- <i>E.coli</i> - <i>S.aureus</i> - <i>P.aeruginosa</i>	[47–51]
Titanium dioxide (TiO₂)	- Formation of superoxide radicals, ROS, and site-specific DNA damage.	- <i>E.coli</i> - <i>S.aureus</i>	[17,52]

3.1. Synthesis of antibacterial nanoparticles.

As shown in Figure 2, nanoparticles can be synthesized using bottom-up or top-down methods [53,54]. The top-down method is based on physical or chemical processes, while combined chemical and biological synthesis are used in bottom-up approaches [55,56]. In the bottom-up approach, NPs are built atom by atom or molecule by molecule. In contrast, in the top-down approach, a large structure is gradually undersized, reaching nanometric dimensions after applying severe mechanical/chemical stresses, strong shocks, and strong deformations.

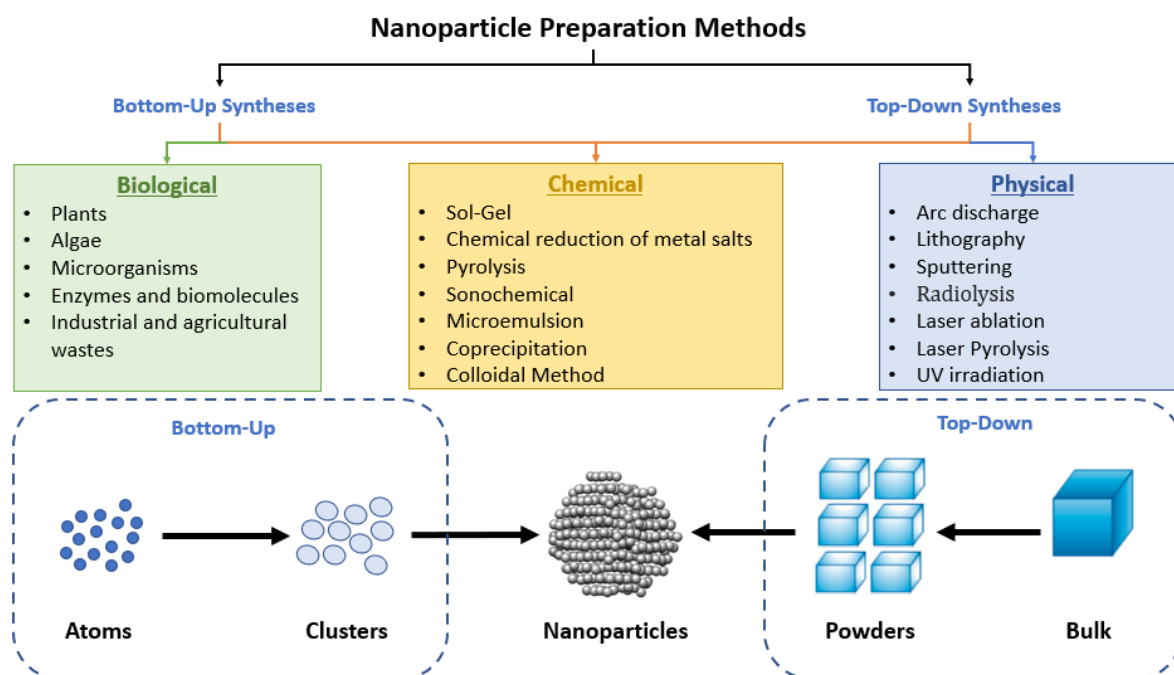


Figure 2. Different approaches and methods for nanoparticle synthesis. Nanoparticles can be synthesized through chemical, physical, and biological routes.

The "bottom-up" approach consists of building nanomaterials atom by atom, molecule by molecule, or aggregate by aggregate. The assembly or positioning of atoms, molecules, or aggregates is carried out precisely, controlled, and exponentially, thus allowing the development of functional materials whose structure is completely controlled [54].

The "top-down" approach stems from microelectronics and consists of reducing and, more precisely, miniaturizing current systems by optimizing existing industrial technologies. Thus, devices and structures are gradually undersized or fractionated until they reach nanometric dimensions. Currently, high-energy grinding is one of the main techniques used in this approach [54].

The two approaches tend to converge in terms of the size range of NPs. The "bottom-up" approach nevertheless seems richer in terms of the type of material, diversity of architecture, and control of the nanometric state, while the "top-down" approach makes it possible to obtain important quantities of material, but the control of the nanometric state turns out to be more delicate.

3.2. Characterization of nanoparticles.

3.2.1. Size measurement.

The most widely used methods are electron microscopy methods, X-ray diffraction, and dynamic light scattering (DLS) [57].

3.2.1.1. Microscopic methods.

Electron microscopy uses an electron beam to image structures that cannot be seen with the naked eye or with optical microscopy. Two methods of electron microscopy are mainly used:

- Scanning electron microscopy (SEM).

Among various electron microscopy techniques, SEM is a surface imaging method fully capable of resolving different particle sizes, size distributions, nanomaterial shapes, and the surface morphology of the synthesized particles at the micro and nanoscales [58,59]. The disadvantage of SEM is that with this technique, we cannot identify the particle's internal structure, but the main advantage is that it can deliver valuable information regarding the purity and degree of particle aggregation [60].

- Transmission electron microscopy (TEM).

The TEM microscopy allows measurements of size, shape, and count as well as the state (agglomerated, aggregated) of nanoparticles with nanometric resolution. TEM has two advantages over SEM: it can provide a better spatial resolution and the capability for additional analytical measurements [61,62]. The disadvantages of TEM include the need for a high vacuum and a large sample section [63].

3.2.1.2. X-ray diffraction (XRD).

X-ray crystallography or X-ray diffraction (X-ray diffraction) is an analysis technique based on the diffraction of X-rays on the matter. Since diffraction only occurs on a crystalline material, we also speak of radio crystallography. Diffraction is one of the elastic scattering methods [64]. This method uses an incident x-ray beam of known wavelength, which encounters the crystal causing the light beam to scatter in specific directions. By measuring the

angles and the intensity of the refracted rays, it is possible to obtain a three-dimensional image of the electron density in the crystal. From this density, we obtain two types of information [65–67]:

- Structural information: Lattice parameters, atom distribution,
- Microstructural information: Grain size.

The disadvantages of this XRD technique are that sometimes there is difficulty in growing the crystals and the ability to get results pertaining only to a single conformation/binding state [68].

3.2.1.3. Light scattering methods.

The static method (SLS): Static light scattering is a technique for measuring absolute molar mass from the relationship between the intensity of light scattered by a molecule and its size and molar mass, as described by Rayleigh's theory. In other words, according to Rayleigh's theory, large molecules scatter more light for a given light source than small ones, and the scattered intensity is proportional to the molar mass of the molecule [69].

The dynamic method (DLS): The DLS consists in measuring the hydrodynamic diameter of the particle. The scattering of light by the particles in the sample is subjected to random thermal movements [69].

3.2.2. Stability of nanoparticles: zeta potential

The measurement of the zeta potential makes it possible to evaluate the stability of colloidal suspensions [70]. Zeta potential is defined by the electrical charge that a particle acquires from the cloud of ions surrounding it when a particle is in motion [71]. The value of zeta potential greater than +30 mV or less than -30 mV means that the colloidal suspension is highly stable [31]. In fact, colloidal suspensions stability and aggregation propensity are issues that should be strongly considered profoundly. Aggregation might cause a substantial decrease in the effective surface area of nanoparticles, which can lead to the reduction or loss of antibacterial activity [72].

3.2.3. Specific surface area.

The specific surface area, defined as the total surface area of a solid material per unit of mass, is an important characteristic of nanoparticles that is partly responsible for their properties. The specific surface area also makes it possible to determine the volume-specific surface area (VSSA) that could replace or complete the size measurement by electronic microcopying [73,74]. The most used technique for determining the specific surface is the Brunauer, Emmett, and Teller method (BET) [75]. This technique models the physical adsorption (physisorption) of gas molecules on a solid surface in a closed system. Physisorption is a phenomenon that occurs in any gas-solid or gas-liquid system when the temperature and pressure conditions are adequate.

Particle size and specific surface area are essential parameters that play a crucial role in interacting nanomaterials with the bacterial surface. As a particle's size decreases, its specific surface area increases, and the number of atoms on the surface becomes more considerable [76]. Nanoparticles became highly active against bacteria due to their antibacterial activity because their large surface area gives for multivalent interactions with the bacterial surface [77].

3.3. Antibacterial mechanisms of NPs.

The lethal mechanism of nanoparticles is still under discussion, but three main mechanisms are assumed (Figure 3), namely; first, the formation of reactive oxygen species (ROS) [19]; second, the ion release process [20]; and, finally, non-oxidative mechanisms [21].

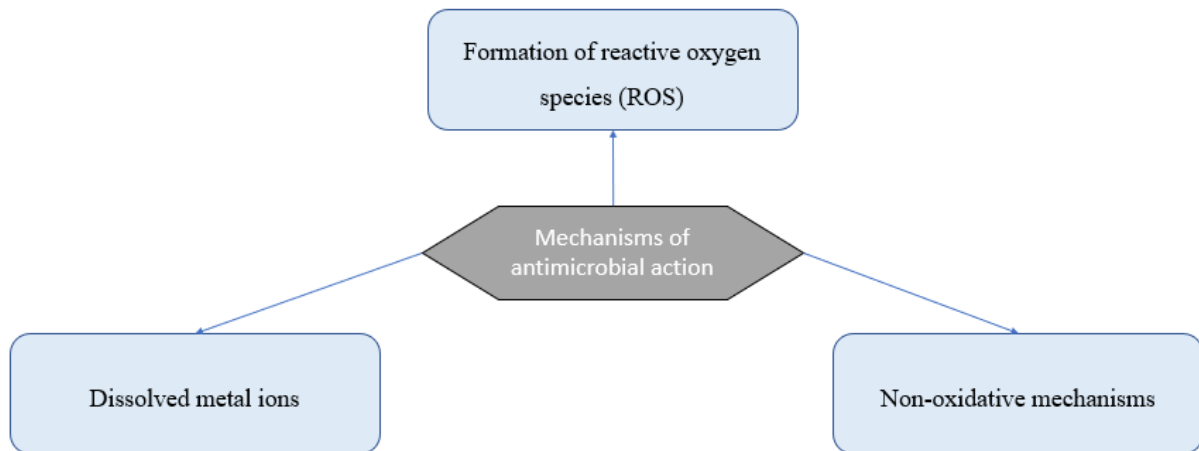


Figure 3. The antibacterial mechanisms of nanoparticles.

3.3.1. Formation of reactive oxygen species (ROS).

Reactive oxidizing species (ROS) production by nanoparticles plays an important role in their antibacterial efficacy. The level of ROS production induced by NPs is controlled by several factors such as size, shape, surface, solubility, aggregation, composition, and particle uptake [7,78,79]. Metal and metal oxide NPs usually produce reactive oxygen species (ROS) by releasing metallic ions that alter the cellular components of bacteria [80,81]. ROS are made up of short-lived oxidants, such as superoxide radicals (O_2^-), hydrogen peroxide (H_2O_2), hydroxyl radicals ($\bullet OH$), and singlet oxygen ($O_2 \bullet$) [82,83]. Due to the high reactivity of these species, ROS can damage (1) cell membrane, resulting in membrane rupture and cell death [84]. Furthermore, excessive cellular ROS could cause damage to (2) mitochondria, which is a known trigger of the apoptotic pathway [85]. In addition, ROS could cause (3) nucleic acid damage [86] and can also be the origin of (4) protein damage, leading to vitiation and/or abolition of protein functions [87] (Figure 4).

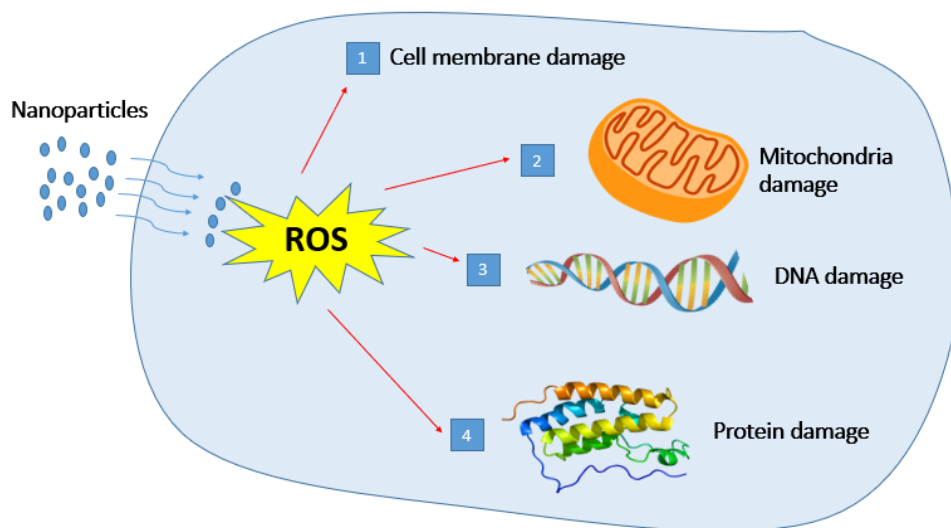


Figure 4. Schematic representation of ROS mechanisms of NPs against bacteria.

Potential antibacterial properties of some metal and metal oxide NPs (such as silver [Ag] nanoparticles, titanium dioxide [TiO₂], and zinc dioxide [ZnO]) have been widely reported against both Gram-negative and Gram-positive bacteria [5,88–91]. For example, silver nanoparticles can generate high amounts of ROS: singlet oxygen, hydroxyl radical, superoxide anion, hypochlorous acid, and hydrogen peroxide [92]. Whereas zinc oxide NPs can generate hydrogen peroxide and hydroxyl radicals but not superoxide radicals [8]. In addition, TiO₂ NPs can produce ROS—such as hydroxyl radical ($\cdot\text{OH}$), singlet oxygen (O₂), and hydrogen peroxide (H₂O₂)—being generated [93].

3.3.2. Dissolved metal ions.

Metal ions are slowly released from the metal oxide and are absorbed through the cell membrane, followed by direct interaction with functional groups such as [mercapto (–SH), amino (–NH), and carboxyl (–COOH)]. These interactions have several consequences, including damaging enzymatic activity, modification of physiological processes, and inhibition of microorganisms [94]. A study by Polivkova *et al.* showed that silver nanowires release silver ions in solution and also have antibacterial effects [95]. However, other studies have suggested that the main antimicrobial mechanism of NPs is not due to the release of metal ions from NPs, as solutions of metal ions cause only weak antibacterial activity [96,97].

3.3.3. Non-oxidative mechanisms.

The non-oxidative mechanism involves the direct interaction of nanoparticles with bacterial membranes or cell walls. The non-oxidative mechanism also affects the inactivation of microbes by decreasing the critical cellular metabolism such as protein, amino acid metabolism, nucleotide metabolism, energy metabolism, and carbohydrate metabolism without oxidative stress induction. Leung and colleagues demonstrated the antimicrobial activity of three types of nanoparticles (MgO-NPs) against *E. coli* [21]. The three types of MgO NPs have been confirmed to have good antibacterial effects on *E. coli* under UV and natural light. However, these antibacterial mechanisms of NPs are unrelated to membrane lipid peroxidation caused by oxidative stress [21].

3.4. Examples of nanoparticles with antibacterial activity.

Several metal or metal oxide NPs, such as silver (Ag) NPs, zinc oxide (ZnO) NPs, and titanium dioxides (TiO₂) NPs, are known to have antimicrobial activities against both Gram-positive bacteria and Gram-negative bacteria.

Silver NPs (AgNPs): silver nanoparticles are recognized as a promising strategy against several Gram-negative and Gram-positive species, such as *P. aeruginosa*, *S. aureus*, and *E. coli*, since it disrupts both cell wall and metabolic pathways [98,99]. Several authors have reported that the antibacterial activity of AgNPs is influenced by the size of the NP. Antibacterial activity increases upon reduction of their particle size due to the increase in the surface area, which allows greater contact with bacterial cells [45,100,101]. The antibacterial activity of AgNPs with sizes (5 to 20 nm) has a strong antimicrobial activity against *S. aureus* [102]. AgNPs exhibited high bactericidal activity against multidrug-resistant *Pseudomonas aeruginosa*, and ampicillin-resistant *E. coli* O157:H7. The minimum inhibition concentration (MIC) was found to be 83.3 mM for *P. aeruginosa* and *E. coli* O157:H7 [103]. Increasing scientific evidence has demonstrated that AgNPs activity depends not only on their size [104]

but also on their shape. The shape is the other parameter of NPs that are responsible for the interaction with the bacterial cell wall. Truncated triangular-shaped silver nanoparticles exhibited higher antibacterial activity against *E. coli* bacteria rather than spherical and rod-shaped NPs [105,106].

Zinc Oxide (ZnO) NPs: ZnO NPs fight against bacteria [106], fungi [107], and viruses [108]. The mechanism of ZnO NPs' antimicrobial activity involves the liberation of antimicrobial ions, mainly Zn²⁺ ions [109–111], and the generation of reactive oxygen species [112,113]. ZnO generates highly reactive oxygen species such as hydrogen peroxide (H₂O₂) and OH[•]. Hydrogen peroxide generated on the surface of ZnO can penetrate bacterial cells and effectively inhibit cell growth [48]. However, Zn²⁺ ions released from the ZnO NPs significantly affect the damage of the cell membrane, the active transport inhibition, the amino acid metabolism, and the enzyme system disruption. Kasemets *et al.* [109] have shown that the release of Zn²⁺ ions was a logical cause of ZnO toxicity toward *Saccharomyces cerevisiae* cells [114]. Previous studies have indicated that ZnO NPs exhibit antibacterial activity against *E. coli*, *Listeria monocytogenes*, *Salmonella*, and *Staphylococcus aureus* [18,49].

Titanium Dioxide (TiO₂) NPs: TiO₂ is a non-toxic and chemically stable molecule with specific optical properties [97] and has significant antibacterial activity against certain microbes [115]. The antimicrobial activity of TiO₂ is due to its size, crystalline structure, and shape [116]. Anatase has the most antibacterial activity among the three crystal structures (anatase, brookite, and rutile). Anatase structures produce hydroxyl radical (•OH) via a photocatalytic reaction, puncturing the bacterial wall and killing the bacteria. Besides, the antibacterial properties of nanoscaled titanium are also related to its photocatalytic properties. It was demonstrated, *in vitro*, that TiO₂-mediated photocatalytic had microbial activity against facultative anaerobes (*E. coli*, *S. aureus*) and obligate aerobes (*P. aeruginosa*) [117]. Like other metal oxides, TiO₂ acts on bacteria by forming reactive oxygen species (ROS) [118]. The ROS synergistically acts on phospholipids on the surface of bacteria [119], causing site-specific DNA damage [17].

3.5. Anti-quorum sensing activity of nanoparticles.

Quorum sensing (QS) is a mode of bacterial communication that allows bacteria to synchronize their genetic expressions according to their cell densities through the production, release, accumulation, and detection of small signal molecules called autoinducers (AIs) [120,121]. For example, Gram-positive bacteria produce autoinducing peptides (AIPs), whereas Gram-negative bacteria produce acyl-homoserine lactone (acyl-HSLs) signal molecules. These signal molecules (AIs) stimulate the expression of QS several genes that lead to many bacterial functions such as biofilm formation, virulence factor production, antibiotic resistance, bioluminescence, biosurfactant production, swarming, etc. [122].

Targeting QS systems in bacterial pathogens is a promising strategy to control bacterial virulence and biofilm formation without impeding bacterial growth [120]. Several quorum quenching (QQ) strategies have been proposed (as illustrated in Figure 5) to disrupt cell-to-cell communication by inhibiting the synthesis of signaling molecules, degradation of a signaling molecule, inhibition of signaling molecule-receptor complex formation, and inhibition of expression of QS-regulated genes [123–125].

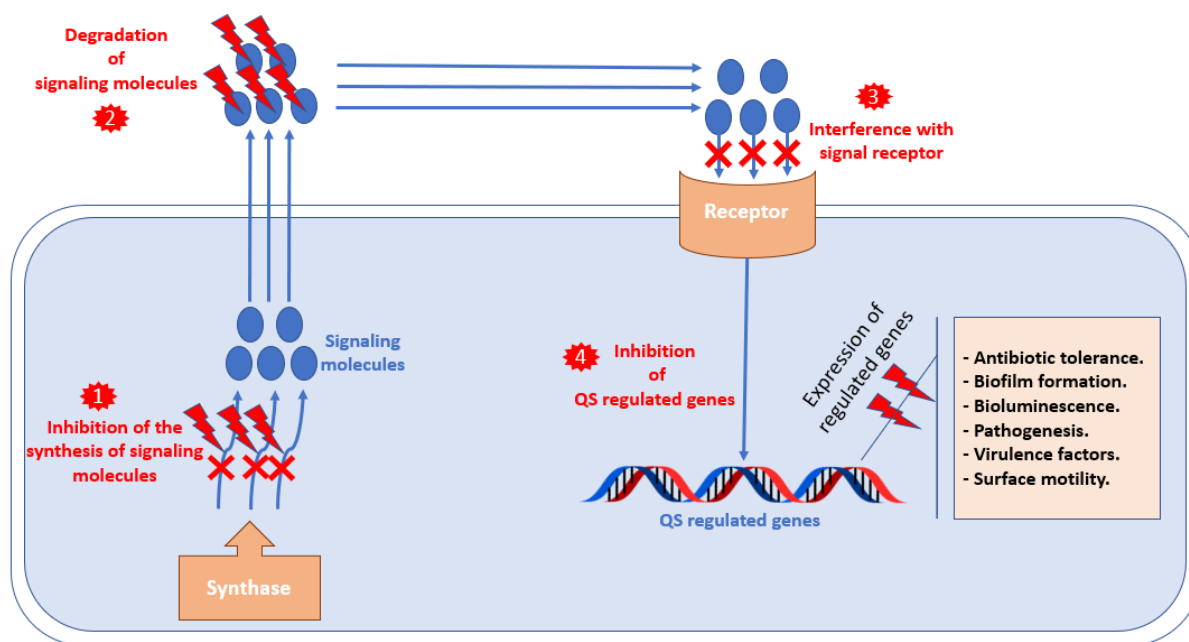


Figure 5. Schematic representation of anti-quorum sensing mechanisms of nanoparticles.

The recent advancement in nanotechnology has facilitated the development of novel nano-antimicrobials targeting the QS mechanism with less toxicity and improved therapeutic potential (Table 2). Ali *et al.* [126] reported that AgNPs have the potential to block the synthesis of N-acyl homoserine lactones (signaling molecules) by inhibiting LasI/RhlI synthase. AgNPs had the potential to inhibit the quorum sensing of *P. aeruginosa*. Saleh, M. M. *et al.* [127] revealed that ZnO nanoparticles had a statistically significant reduction in the production of QS-controlled virulence factors such as rhamnolipids, pyoverdin, pyocyanin, hemolysins, proteases, and elastase. Furthermore, ZnO nanoparticles exhibited a significant down-regulate the relative of QS-regulatory genes lasI, lasR, rhlI, rhlR, pqsA and pqsR. Similar results have been obtained by Singh *et al.* [128] that silver nanoparticles down-regulated the expression of quorum-sensing-regulatory genes lasI, lasR, rhlI, and rhlR. In another study, Garcia-Lara *et al.* [129] reported that ZnO NPs could significantly reduce the secretion of quorum-sensing dependent pyocyanin and elastase and the production of biofilm in *P. aeruginosa*.

Table 2. Metals and metal oxide nanoparticles demonstrate anti-QS activity and their mode of action.

Nanoparticles	Test organism	Mode of action	References
Silver NPs (AgNPs)	<i>P. aeruginosa</i> (Gram-negative)	- Inhibition of LasI/RhlI synthase blocked the biosynthesis of N-acyl homoserine lactones (AHLs); thus, no AHL was produced, and no QS occurred. (<i>In silico</i> approach)	[126]
		- Molecular modeling and docking studies showed that silver nanoparticles had the potential to inhibit key enzymes (LasR, Vfr, QscR, RhlR, and PqsA) that are involved in QS.	[130]
		The AgNPs efficiently inhibited the production of quorum sensing mediated virulence factors viz. protease, pyocyanin, hemolysin, and biofilm formation by <i>P. aeruginosa</i> .	[131]
	<i>S. aureus</i> (Gram-positive)	- The silver nanoparticles effectively inhibited the quorum-sensing mediated biofilm formation in <i>S. aureus</i> .	[132]
	<i>C.violaceum</i> (Gram-negative)	- Inhibition of violacein and alginate productions was reduced by 89.6 and 75.6% at 4 and 8 µg/mL of silver nanoparticles, suggesting anti-quorum sensing activity. (<i>In vitro</i> approach)	[130]
<i>P. mirabilis</i> and <i>S. marcescens</i> (Gram-negative)	- The <i>Piper betle</i> -based synthesized silver nanoparticles (NPs) could inhibit QS-regulated virulence factors such as prodigiosin, protease, biofilm formation, hydrophobicity, and exopolysaccharides production in uropathogenic. - The gene expression analysis disclosed that silver nanoparticles downregulation the expression of <i>flhD</i> and <i>bsmB</i> genes in <i>S. marcescens</i> and <i>flhD</i> and <i>rsbA</i> genes in <i>P. mirabilis</i> .	[133]	

Nanoparticles	Test organism	Mode of action	References
Zinc Oxide (ZnO) NPs	<i>P. aeruginosa</i> (Gram-negative)	- The interaction of ZnO NPs with the QS (Las/Rhl) systems of <i>P. aeruginosa</i> led to the inactivation of autoinducers such as N-acyl homoserine lactone (AHL) molecules, which ultimately led to QS inactivation and down-regulation negative of virulence determinants. (<i>In silico</i> approach)	[134]
		- The ZnO NPs effectively inhibited the growth and quorum-sensing mediated virulence in <i>P. aeruginosa</i> , such as swarming, swimming, and biofilm formation. (<i>In vitro</i> approach)	
		- Synthesized ZnO nanostructures significantly inhibited QS-regulated functions of <i>C. violaceum</i> CVO26 (violacein) and protease, elastase, alginate, and pyocyanin production in <i>P. aeruginosa</i> PAO1 significantly.	[135]
		- The ZnO nanoparticles inhibit biofilm formation and pyocyanin production without affecting the growth of planktonic cells.	[136]
	- The ZnO nanoparticles showed inhibition of the production of QS-controlled virulence factors pyocyanin, rhamnolipids, pyoverdine, hemolysins, proteases, and elastase.	[127]	
	<i>C. violaceum</i> (Gram-negative)	- The ZnO nanoparticles lowered the expression of the genes responsible for quorum sensing in <i>C. violaceum</i> , bringing about inhibition of N-acyl homoserine lactone (AHL) synthase, and in response blocking quorum sensing in <i>C. violaceum</i> .	[137]
Titanium Dioxide (TiO ₂) NPs	<i>P. aeruginosa</i> (Gram-negative)	- Titanium dioxide nanoparticles showed a significant reduction in biofilm formation of <i>P. aeruginosa</i> strains (96%) and also a reduction in the expression of genes regulated by quorum sensing (<i>lasR</i> , <i>lasI</i> , <i>rhlR</i> , <i>rhlI</i> , <i>pqsA</i> , <i>pqsR</i>).	[138]

Targeting quorum sensing and biofilm formation by metals and metal oxide nanoparticles can be used as a novel strategy in developing antibacterial agents that can counter cell-to-cell communication, prevent biofilm production, bypass resistance to antibacterial agents, and prevent bacterial infections.

4. Nanoparticles databases

An overview of nanomaterials databases is provided in Table 3. The emergence of recent databases such as caNanoLab (cancer Nanotechnology Laboratory), eNanoMapper, Nanomaterial Registry (NR), Nanoparticle Information Library (NIL), and PubVINAS seems encouraging and is discussed below [139–143].

The caNanoLab is a database created by the National Cancer for sharing information within the international biomedical nanotechnology research community to accelerate and validate the use of nanoparticles in biomedicine. The caNanoLab contains detailed information on characterizations (physicochemical, *in vitro*, *in vivo*, and *ex vivo*), composition, experimental design, and publications of nanoparticles. The physicochemical properties of nanoparticles include size, shape, composition, purity, molecular weight, and surface area. In addition, experimental biological data such as genotoxicity, oxidative stress, cytotoxicity, immunotoxicity, and pharmacokinetics are collected in this database [144].

The eNanoMapper is an online database hosting nanoparticle characterization data and biological and toxicological information. In eNanoMapper, physicochemical properties such as stability, size distribution, zeta potential, surface area, freezing/melting point, shape, and aspect ratio are included. eNanoMapper also contains a variety of toxicological experimental data such as immunotoxicity, cell viability, genetic toxicity, and oxidative stress [145].

The Nanomaterial Registry (NR) is a public and wholly curated database that is funded by the National Institutes of Health (NIH). It archives experimental data such as physicochemical characteristics such as composition, size, shape, surface area, surface chemistry, solubility, stability, aggregation/agglomeration state, surface charge, and size distribution), and studies on biological interactions and environmental interactions studies of

nanoparticles. In this database, the nanomaterials can be browsed by their material type (for example, carbon, polymer, metal, metal oxide), size (for example, less than 25 nm, 25–74 nm, 75–149 nm, 150–300 nm, and greater than 300 nm), shape (1D, 2D, and 3D), or surface area (for example less than 10 m²/g, 10–49 m²/g, 50 - 150 m²/g, greater than 150 m²/g) [146].

The Nanoparticle Information Library (NIL) is a prototype searchable data resource on nanoparticle properties associated with nanoparticle health and safety. It contains information on nanomaterial composition, production method, surface area, particle size, morphology including scanning, transmission, or other electron micrographic images, availability for research or commercial applications, and associated or relevant nanoparticle publications [145].

The PubVINAS is a nanoparticles database that contains several types of nanoparticles such as silver nanoparticles (AgNPs), metal oxide nanoparticles (MONPs), gold nanoparticles (GNPs), platinum nanoparticles (PtNPs), palladium nanoparticles (PdNPs), quantum dot nanoparticles, DNA origami nanoparticles (DnaNPs), and carbon nanoparticles. The PubVINAS contains the physicochemical properties (size, shape, number of ligands, log P, and zeta potential) and biological activities (cytotoxicity, cell uptake, cell viability, cell association, and oxidative stress) of nanoparticles [147].

Table 3. Databases of nanoparticles.

Database	Website	Description
caNanoLab	https://cananolab.nci.nih.gov/	- Nanotechnology in biomedicine
eNanoMapper	https://data.enanomapper.net/	- Safety assessment of nanomaterials
Nanomaterial Registry (NR)	https://nanomaterialregistry.net/	- Physico-chemical properties - Biological interaction studies - Environmental interaction studies
Nanoparticle Information Library (NIL)	http://nanoparticlelibrary.net/	- Physicochemical characteristics
PubVINAS	http://www.pubvinas.com/	- Physico-chemical properties

The databases presented above provide a solid foundation to support data analysis on nanoparticles' physical, chemical, and biological properties, but they currently house small amounts of data. This could be partly due to the inefficiency of data-sharing and collection processes. This reflects a discrepancy between the data generated in the researchers' laboratories and those available in the databases.

5. Conclusions

The evolution of bacterial resistance to antimicrobial agents poses a great global public health problem, and new antimicrobial agents are urgently sought to address this problem. Innovative advances in nanotechnology, particularly nanoparticle engineering, are likely to lead to the development of new antibacterial agents. Different research groups have developed several such nanoparticles, and their antimicrobial activity, anti-quorum sensing, and anti-biofilm have been tested on Gram-positive and Gram-negative bacteria. However, the advantages of NPs are the same reasons that make them dangerous, small size, surface properties, and aggregation. Therefore, research into nanoparticles is currently one of the most studied branches of science due to the almost unlimited fields of application.

Publicly accessible databases are core resources for data-rich research, consolidating field-specific knowledge and highlighting best practices and challenges. Further effective growth of nanoparticle databases requires the concerted efforts of database stewards, the research community, journal publishers, and funding agencies.

Funding

Research and development project within the framework of Moroccan-Tunisian cooperation 2020-2023. Title: New application of nanoparticles with antibacterial effect: Elaboration of bioactive paint for hospitals.

Acknowledgments

This research has no acknowledgment.

Conflicts of Interest

The authors declare no conflict of interest.

References

1. Prestinaci, F.; Pezzotti, P.; Pantosti, A. Antimicrobial Resistance: A Global Multifaceted Phenomenon. *Pathog. Glob. Health* **2015**, *109*, 309–318, <https://doi.org/10.1179/2047773215Y.0000000030>.
2. Rai, M.; Deshmukh, S.; ... A.I.-J. of applied; 2012, Silver Nanoparticles: The Powerful Nanoweapon against Multidrug-resistant Bacteria. *Wiley Online Libr.* **2012**, *112*, 841–852, <https://doi.org/10.1111/j.1365-2672.2012.05253.x>.
3. Awad, H.; ELâ, K.; Aziz, R.; Sarmidi, M.; Jurnal, H.E. Antibiotics as Microbial Secondary Metabolites: Production and Application. *journals.utm.my*, **2012**, *59*, <https://doi.org/10.11113/jt.v59.1593>.
4. Rudramurthy, G.R.; Swamy, M.K.; Sinniah, U.R.; Ghasemzadeh, A. Nanoparticles: Alternatives against Drug-Resistant Pathogenic Microbes. *Molecules* **2016**, *21*, <https://doi.org/10.3390/molecules21070836>.
5. Hajipour, M.J.; Fromm, K.M.; Ashkarran, A.A.; de Aberasturi, D.J.; de Larramendi, I.R.; Rojo, T.; Serpooshan, V.; Parak, W.J.; Mahmoudi, M. Antibacterial Properties of Nanoparticles. *Elsevier*. **2012**, *30*, 499-511, <https://doi.org/10.1016/j.tibtech.2012.06.004>.
6. Whitesides, G.M. Nanoscience, Nanotechnology, and Chemistry. *Small* **2005**, *1*, 172–179, <https://doi.org/10.1002/SMLL.200400130>.
7. Jeevanandam, J.; Barhoum, A.; Chan, Y.S.; Dufresne, A.; Danquah, M.K. Review on Nanoparticles and Nanostructured Materials: History, Sources, Toxicity and Regulations. *Beilstein J. Nanotechnol.* **2018**, *9*, 1050-1074, <https://doi.org/10.3762/bjnano.9.98>.
8. Wang, L.; Hu, C.; Shao, L. The Antimicrobial Activity of Nanoparticles: Present Situation and Prospects for the Future. *Int. J. Nanomedicine* **2017**, *12*, 1227–1249, <https://doi.org/10.2147/IJN.S121956>.
9. Jadhav, K.; Deore, S.; Dhamecha, D.; Hr, R.; Jagwani, S.; Jalalpure, S.; Bohara, R. Phytosynthesis of Silver Nanoparticles: Characterization, Biocompatibility Studies, and Anticancer Activity. *ACS Biomater. Sci. Eng.* **2018**, *4*, 892–899, <https://doi.org/10.1021/ACSBiomaterials.7B00707>.
10. Vijayakumar, S.; Krishnakumar, C.; Arulmozhi, P.; Mahadevan, S.; Parameswari, N. Biosynthesis, Characterization and Antimicrobial Activities of Zinc Oxide Nanoparticles from Leaf Extract of *Glycosmis Pentaphylla* (Retz.) DC. *Microbial pathogenesis* **2018**, *116*, 44-48, <https://doi.org/10.1016/j.micpath.2018.01.003>.
11. Moeinzadeh, S.; Jabbari, E. Nanoparticles and Their Applications. *Springer Handbooks* **2017**, 335–361, https://doi.org/10.1007/978-3-662-54357-3_11.
12. Visai, L.; de Nardo, L.; Punta, C.; Melone, L.; Cigada, A.; Imbriani, M.; Arciola, C.R. Titanium Oxide Antibacterial Surfaces in Biomedical Devices. *Int. J. Artif. Organs* **2011**, *34*, 929- 946, <https://doi.org/10.5301/ijao.5000050>.
13. Mishra, A.; Tripathy, S.K.; Yun, S. II Bio-Synthesis of Gold and Silver Nanoparticles from *Candida Guilliermondii* and Their Antimicrobial Effect against Pathogenic Bacteria. *In Proceedings of the Journal of Nanoscience and Nanotechnology*, **2011**, *11*, 243-248, <https://doi.org/10.1166/jnn.2011.3265>.
14. Surwade, P.; Ghildyal, C.; Weikel, C.; Luxton, T.; Peloquin, D.; Fan, X.; Shah, V. Augmented Antibacterial Activity of Ampicillin with Silver Nanoparticles against Methicillin-Resistant *Staphylococcus Aureus* (MRSA). *J. Antibiot. (Tokyo)*. **2019**, *72*, <https://doi.org/10.1038/s41429-018-0111-6>.
15. Yuwen, L.; Sun, Y.; Tan, G.; Xiu, W.; Zhang, Y.; Weng, L.; Teng, Z.; Wang, L. MoS₂@polydopamine-Ag Nanosheets with Enhanced Antibacterial Activity for Effective Treatment of *Staphylococcus Aureus* Biofilms and Wound Infection. *Nanoscale* **2018**, *10*, <https://doi.org/10.1039/c8nr04111c>.
16. Crisan, C.M.; Mocan, T.; Manolea, M.; Lasca, L.I.; Tăbăran, F.A.; Mocan, L. Review on Silver Nanoparticles as a Novel Class of Antibacterial Solutions. *Appl. Sci.* **2021**, *11*, 1120, <https://doi.org/10.3390/app11031120>.
17. Besinis, A.; De Peralta, T.; Handy, R.D. The Antibacterial Effects of Silver, Titanium Dioxide and Silica

- Dioxide Nanoparticles Compared to the Dental Disinfectant Chlorhexidine on Streptococcus Mutans Using a Suite of Bioassays. *Nanotoxicology* **2014**, *8*, <https://doi.org/10.3109/17435390.2012.742935>.
18. Tayel, A.A.; El-Tras, W.F.; Moussa, S.; El-Baz, A.F.; Mahrous, H.; Salem, M.F.; Brimer, L. Antibacterial Action of Zinc Oxide Nanoparticles against Foodborne Pathogens. *J. Food Saf.* **2011**, *31*, <https://doi.org/10.1111/j.1745-4565.2010.00287.x>.
 19. Gurunathan, S.; Han, J.W.; Abdal Dayem, A.; Eppakayala, V.; Kim, J.H. Oxidative Stress-Mediated Antibacterial Activity of Graphene Oxide and Reduced Graphene Oxide in *Pseudomonas Aeruginosa*. *Int. J. Nanomedicine* **2012**, *7*, <https://doi.org/10.2147/IJN.S37397>.
 20. Nagy, A.; Harrison, A.; Sabbani, S.; Munson, R.S.; Dutta, P.K.; Waldman, W.J. Silver Nanoparticles Embedded in Zeolite Membranes: Release of Silver Ions and Mechanism of Antibacterial Action. *Int. J. Nanomedicine* **2011**, *6*, 1833-1852, <https://doi.org/10.2147/ijn.s24019>.
 21. Leung, Y.H.; Ng, A.M.C.; Xu, X.; Shen, Z.; Gethings, L.A.; Wong, M.T.; Chan, C.M.N.; Guo, M.Y.; Ng, Y.H.; Djurišić, A.B.; *et al.* Mechanisms of Antibacterial Activity of Mgo: Non-Ros Mediated Toxicity of Mgo Nanoparticles towards *Escherichia Coli*. *Small* **2014**, *10*, <https://doi.org/10.1002/sml.201302434>.
 22. Velázquez-Velázquez, J.L.; Santos-Flores, A.; Araujo-Meléndez, J.; Sánchez-Sánchez, R.; Velásquillo, C.; González, C.; Martínez-Castañón, G.; Martínez-Gutierrez, F. Anti-Biofilm and Cytotoxicity Activity of Impregnated Dressings with Silver Nanoparticles. *Mater. Sci. Eng. C* **2015**, *49*, <https://doi.org/10.1016/j.msec.2014.12.084>.
 23. Singh, B.N.; Prateeksha; Upreti, D.K.; Singh, B.R.; Defoirdt, T.; Gupta, V.K.; De Souza, A.O.; Singh, H.B.; Barreira, J.C.M.; Ferreira, I.C.F.R.; *et al.* Bactericidal, Quorum Quenching and Anti-Biofilm Nanofactories: A New Niche for Nanotechnologists. *Crit. Rev. Biotechnol.* **2017**, *37*, 525-540, <https://doi.org/10.1080/07388551.2016.1199010>.
 24. Gómez-Gómez, B.; Arregui, L.; Serrano, S.; Santos, A.; Pérez-Corona, T.; Madrid, Y. Unravelling Mechanisms of Bacterial Quorum Sensing Disruption by Metal-Based Nanoparticles. *Sci. Total Environ.* **2019**, *696*, <https://doi.org/10.1016/j.scitotenv.2019.133869>.
 25. Akther, T.; Khan, M.S.; S., H. Biosynthesis of Silver Nanoparticles via Fungal Cell Filtrate and Their Anti-Quorum Sensing against *Pseudomonas Aeruginosa*. *J. Environ. Chem. Eng.* **2020**, *8*, <https://doi.org/10.1016/j.jece.2020.104365>.
 26. Husain, F.M.; Zia, Q.; Khan, M.F.; Ahmad, E.; Jamal, A.; Alaidarous, M.; Banawas, S.; Alam, M.M.; Alshehri, B.A.; Jameel, M.; *et al.* Anti-Quorum Sensing and Anti-Biofilm Activity of Zinc Oxide Nanospikes. *ACS Omega* **2020**, *5*, <https://doi.org/10.1021/acsomega.0c03634>.
 27. Gu, X.; Xu, Z.; Gu, L.; Xu, H.; Han, F.; Chen, B.; Pan, X. Preparation and Antibacterial Properties of Gold Nanoparticles: A Review. *Environ. Chem. Lett.* **2021**, *19*, 167-187, <https://doi.org/10.1007/s10311-020-01071-0>
 28. Ealias, A.M.; Saravanakumar, M.P. A Review on the Classification, Characterisation, Synthesis of Nanoparticles and Their Application. In Proceedings of the IOP Conference Series: *Materials Science and Engineering* **2017**, *263*, <https://iopscience.iop.org/article/10.1088/1757-899X/263/3/032019/meta>.
 29. Nikam, A. V.; Prasad, B.L.V.; Kulkarni, A.A. Wet Chemical Synthesis of Metal Oxide Nanoparticles: A Review. *CrystEngComm* **2018**, *20*, <https://doi.org/10.1039/C8CE00487K>.
 30. Gharpure, S.; Akash, A.; Ankamwar, B. A Review on Antimicrobial Properties of Metal Nanoparticles. *J. Nanosci. Nanotechnol.* **2019**, *20*, <https://doi.org/10.1166/jnn.2020.17677>.
 31. Slavin, Y.N.; Asnis, J.; Häfeli, U.O.; Bach, H. Metal Nanoparticles: Understanding the Mechanisms behind Antibacterial Activity. *J. Nanobiotechnology* **2017**, *15*, 1-20, <https://jnanobiotechnology.biomedcentral.com/articles/10.1186/s12951-017-0308-z>.
 32. Fernando, S.; Gunasekara, T.; Holton, J. Antimicrobial Nanoparticles: Applications and Mechanisms of Action. *Sri Lankan J. Infect. Dis.* **2018**, *8*, <https://doi.org/10.4038/sljid.v8i1.8167>.
 33. Stanić, V.; Tanasković, S.B. Antibacterial Activity of Metal Oxide Nanoparticles. In *Nanotoxicity: Prevention and Antibacterial Applications of Nanomaterials* **2020**, <https://doi.org/10.1016/B978-0-12-819943-5.00011-7>.
 34. Breathnach, A.S. Nosocomial Infections and Infection Control. *Med. (United Kingdom)* **2013**, *41*, 649-653, <https://doi.org/10.1016/j.mpm.2013.08.010>.
 35. Campoccia, D.; Montanaro, L.; Arciola, C.R. The Significance of Infection Related to Orthopedic Devices and Issues of Antibiotic Resistance. *Biomaterials* **2006**, *27*, <https://doi.org/10.1016/j.biomaterials.2005.11.044>.
 36. Klevens, R.M.; Morrison, M.A.; Nadle, J.; Petit, S.; Gershman, K.; Ray, S.; Harrison, L.H.; Lynfield, R.; Dumyati, G.; Townes, J.M.; *et al.* Invasive Methicillin-Resistant *Staphylococcus Aureus* Infections in the United States. *J. Am. Med. Assoc.* **2007**, *298*, <https://doi.org/10.1001/jama.298.15.1763>.
 37. Fischbach, M.A.; Walsh, C.T. Antibiotics for Emerging Pathogens. *Science (80-.)* **2009**, *325*, 1089- 1093, <https://doi.org/10.1126/science.1176667>.
 38. Huh, A.J.; Kwon, Y.J. "Nanoantibiotics": A New Paradigm for Treating Infectious Diseases Using Nanomaterials in the Antibiotics Resistant Era. *J. Control. Release* **2011**, *156*, 128-145, <https://doi.org/10.1016/j.jconrel.2011.07.002>
 39. Chen, C.W.; Hsu, C.Y.; Lai, S.M.; Syu, W.J.; Wang, T.Y.; Lai, P.S. Metal Nanobullets for Multidrug

- Resistant Bacteria and Biofilms. *Adv. Drug Deliv. Rev.* **2014**, *78*, 88-104, <https://doi.org/10.1016/j.addr.2014.08.004>.
40. Balderrama-González, A.S.; Piñón-Castillo, H.A.; Ramírez-Valdespino, C.A.; Landeros-Martínez, L.L.; Orrantia-Borunda, E.; Esparza-Ponce, H.E. Antimicrobial Resistance and Inorganic Nanoparticles. *Int. J. Mol. Sci.* **2021**, *22*, 12890. <https://doi.org/10.3390/ijms222312890>.
 41. Laurent, S.; Mahmoudi, M. Superparamagnetic Iron Oxide Nanoparticles: Promises for Diagnosis and Treatment of Cancer. *Int. J. Mol. Epidemiol. Genet.* **2011**, *2*, 367, <https://doi.org/10.1021/cn100100e>.
 42. Moore, M.N. Do Nanoparticles Present Ecotoxicological Risks for the Health of the Aquatic Environment? *Environ. Int.* **2006**, *32*, <https://doi.org/10.1016/j.envint.2006.06.014>.
 43. Wahajuddin; Arora, S. Superparamagnetic Iron Oxide Nanoparticles: Magnetic Nanoplatforms as Drug Carriers. *Int. J. Nanomedicine* **2012**, *7*, 3445, <https://doi.org/10.2147/IJN.S30320>.
 44. Dastjerdi, R.; Montazer, M. A Review on the Application of Inorganic Nano-Structured Materials in the Modification of Textiles: Focus on Anti-Microbial Properties. *Colloids Surfaces B Biointerfaces* **2010**, *79*, 5-18, <https://doi.org/10.1016/j.colsurfb.2010.03.029>.
 45. Bruna, T.; Maldonado-Bravo, F.; Jara, P.; Caro, N. Silver Nanoparticles and Their Antibacterial Applications. *Int. J. Mol. Sci.* **2021**, *22*, <https://doi.org/10.3390/ijms22137202>.
 46. Mekkawy, A.I.; El-Mokhtar, M.A.; Nafady, N.A.; Yousef, N.; Hamad, M.; El-Shanawany, S.M.; Ibrahim, E.H.; Elsabahy, M. *In vitro* and *in vivo* Evaluation of Biologically Synthesized Silver Nanoparticles for Topical Applications: Effect of Surface Coating and Loading into Hydrogels. *Int. J. Nanomedicine* **2017**, *12*, <https://doi.org/10.2147/IJN.S124294>.
 47. Abebe, B.; Zereffa, E.A.; Tadesse, A.; Murthy, H.C.A. A Review on Enhancing the Antibacterial Activity of ZnO: Mechanisms and Microscopic Investigation. *Nanoscale Res. Lett.* **2020**, *15*, <https://nanoscalereslett.springeropen.com/articles/10.1186/s11671-020-03418-6>.
 48. Ijaz, M.; Zafar, M.; Islam, A.; Afsheen, S.; Iqbal, T. A Review on Antibacterial Properties of Biologically Synthesized Zinc Oxide Nanostructures. *J. Inorg. Organomet. Polym. Mater.* **2020**, *30*, 2815–2826, <https://doi.org/10.1007/S10904-020-01603-9>.
 49. Hammadi, A.H.; Habeeb, S.A.; Al-Jibouri, L.F.; Hussien, F.H. Synthesis, Characterization and Biological Activity of Zinc Oxide Nanoparticles (ZnO NPs). *Syst. Rev. Pharm.* **2020**, *11*, <https://doi.org/10.31838/srp.2020.5.59>.
 50. Vijayakumar, S.; Vinoj, G.; Malaikozhundan, B.; Shanthi, S.; Vaseeharan, B. Plectranthus Amboinicus Leaf Extract Mediated Synthesis of Zinc Oxide Nanoparticles and Its Control of Methicillin Resistant Staphylococcus Aureus Biofilm and Blood Sucking Mosquito Larvae. *Spectrochim. Acta - Part A Mol. Biomol. Spectrosc.* **2015**, *137*, <https://doi.org/10.1016/j.saa.2014.08.064>.
 51. Aswathanarayan, J.B.; Vittal, R.R. Antimicrobial, Biofilm Inhibitory and Anti-Infective Activity of Metallic Nanoparticles Against Pathogens MRSA and Pseudomonas Aeruginosa PA01. *Pharm. Nanotechnol.* **2017**, *5*, <https://doi.org/10.2174/2211738505666170424121944>.
 52. Hirakawa, K.; Mori, M.; Yoshida, M.; Oikawa, S.; Kawanishi, S. Photo-Irradiated Titanium Dioxide Catalyzes Site Specific DNA Damage via Generation of Hydrogen Peroxide. *Free Radic. Res.* **2004**, *38*, <https://doi.org/10.1080/1071576042000206487>.
 53. Wang, Y.; Xia, Y. Bottom-up and Top-down Approaches to the Synthesis of Monodispersed Spherical Colloids of Low Melting-Point Metals. *Nano Lett.* **2004**, *4*, <https://doi.org/10.1021/nl048689j>.
 54. Madkour, L.H. Synthesis Methods For 2D Nanostructured Materials, Nanoparticles (NPs), Nanotubes (NTs) and Nanowires (NWs). In *Advanced Structured Materials*; **2019**; *116*, https://link.springer.com/chapter/10.1007/978-3-030-21621-4_12.
 55. Gan, P.P.; Li, S.F.Y. Potential of Plant as a Biological Factory to Synthesize Gold and Silver Nanoparticles and Their Applications. *Rev. Environ. Sci. Biotechnol.* **2012**, *11*, <https://link.springer.com/article/10.1007/s11157-012-9278-7>.
 56. Lombardo, D.; Calandra, P.; Pasqua, L.; Magazù, S. Self-Assembly of Organic Nanomaterials and Biomaterials: The Bottom-up Approach for Functional Nanostructures Formation and Advanced Applications. *Materials (Basel)*. **2020**, *13*, <https://doi.org/10.3390/ma13051048>.
 57. Guidance on the Risk Assessment of the Application of Nanoscience and Nanotechnologies in the Food and Feed Chain. *EFSA J.* **2011**, *9*, <https://doi.org/10.2903/j.efsa.2011.2140>.
 58. Fissan, H.; Ristig, S.; Kaminski, H.; Asbach, C.; Eppe, M. Comparison of Different Characterization Methods for Nanoparticle Dispersions before and after Aerosolization. *Anal. Methods* **2014**, *6*, <https://doi.org/10.1039/c4ay01203h>.
 59. Hall, J.B.; Dobrovolskaia, M.A.; Patri, A.K.; McNeil, S.E. Characterization of Nanoparticles for Therapeutics. *Nanomedicine* **2007**, *2*, <https://doi.org/10.2217/17435889.2.6.789>.
 60. Bamal, D.; Singh, A.; Chaudhary, G.; Kumar, M.; Singh, M.; Rani, N.; Mundlia, P.; Sehrawat, A.R. Silver Nanoparticles Biosynthesis, Characterization, Antimicrobial Activities, Applications, Cytotoxicity and Safety Issues: An Updated Review. *Nanomaterials* **2021**, *11*, <https://doi.org/10.3390/nano11082086>.
 61. Williams, D.B.; Carter, C.B. The Transmission Electron Microscope. *Transm. Electron Microsc.* **1996**, *3*–*17*, https://doi.org/10.1007/978-1-4757-2519-3_1.
 62. Lin, P.; Lin, S.; Wang, P.; advances, R.S.-B. undefined Techniques for Physicochemical Characterization

- of Nanomaterials. *Biotechnology advances*. **2014**, 32,711-72, <https://doi.org/10.1016/j.biotechadv.2013.11.006>.
63. Naganthran, A.; Verasoundarapandian, G.; Khalid, F.E.; Masarudin, M.J.; Zulkharnain, A.; Nawawi, N.M.; Karim, M.; Che Abdullah, C.A.; Ahmad, S.A. Synthesis, Characterization and Biomedical Application of Silver Nanoparticles. *Materials* **2022**, *15*, 427, <https://doi.org/10.3390/ma15020427>.
64. Wilson, A.J.C. The Optical Principles of the Diffraction of X-Rays by R.W. James. *Acta Crystallogr.* **1950**, *3*, <https://doi.org/10.1107/s0365110x50001476>.
65. Dorofeev, G.A.; Streletskii, A.N.; Povstugar, I. V.; Protasov, A. V.; Elsukov, E.P. Determination of Nanoparticle Sizes by X-Ray Diffraction. *Colloid J.* **2012**, *74*, <https://doi.org/10.1134/S1061933X12060051>.
66. Kandemir, T.; Kasatkin, I.; Girgsdies, F.; Zander, S.; Kühl, S.; Tovar, M.; Schlögl, R.; Behrens, M. Microstructural and Defect Analysis of Metal Nanoparticles in Functional Catalysts by Diffraction and Electron Microscopy: The Cu/ZnO Catalyst for Methanol Synthesis. *Top. Catal.* **2014**, *57*, <https://doi.org/10.1007/s11244-013-0175-2>.
67. Ingham, B. X-Ray Scattering Characterisation of Nanoparticles. *Crystallogr. Rev.* **2015**, *21*, <https://doi.org/10.1080/0889311X.2015.1024114>.
68. Waseda, Y.; Matsubara, E.; Shinoda, K. *X-Ray Diffraction Crystallography; Introduction, Examples and Solved Problems* **2011**, <https://link.springer.com/book/10.1007/978-3-642-16635-8>.
69. Brar, S.K.; Verma, M. Measurement of Nanoparticles by Light-Scattering Techniques. *TrAC - Trends Anal. Chem.* **2011**, *30*, <https://doi.org/10.1016/j.trac.2010.08.008>.
70. Bhattacharjee, S. DLS and Zeta Potential - What They Are and What They Are Not? *J. Control. Release* **2016**, *235*, <https://doi.org/10.1016/j.jconrel.2016.06.017>.
71. Kaszuba, M.; Corbett, J.; Watson, F.M.N.; Jones, A. High-Concentration Zeta Potential Measurements Using Light-Scattering Techniques. In Proceedings of the Philosophical Transactions of the Royal Society A: *Mathematical, Physical and Engineering Sciences* **2010**; 368, <https://doi.org/10.1098/rsta.2010.0175>.
72. Rónavári, A.; Béltéky, P.; Boka, E.; Zakupszky, D.; Igaz, N.; Szerencsés, B.; Pfeiffer, I.; Kónya, Z.; Kiricsi, M. Polyvinyl-Pyrrolidone-Coated Silver Nanoparticles—The Colloidal, Chemical and Biological Consequences of Steric Stabilization under Biorelevant Conditions. *Int. J. Mol. Sci.* **2021**, *22*, <https://doi.org/10.3390/ijms22168673>.
73. Lecloux, A.J.; Atluri, R.; Kolen'ko, Y. V.; Deepak, F.L. Discussion about the Use of the Volume Specific Surface Area (VSSA) as a Criterion to Identify Nanomaterials According to the EU Definition. Part Two: Experimental Approach. *Nanoscale* **2017**, *9*, <https://doi.org/10.1039/c7nr02585h>.
74. Dazon, C.; Witschger, O.; Bau, S.; Fierro, V.; Llewellyn, P.L. Nanomaterial Identification of Powders: Comparing Volume Specific Surface Area, X-Ray Diffraction and Scanning Electron Microscopy Methods. *Environ. Sci. Nano* **2019**, *6*, <https://doi.org/10.1039/C8EN00760H>.
75. Brunauer, S.; Emmett, P.H.; Teller, E. Adsorption of Gases in Multimolecular Layers. *J. Am. Chem. Soc.* **1938**, *60*, <https://doi.org/10.1021/ja01269a023>.
76. Navarro, E.; Baun, A.; Behra, R.; Hartmann, N.B.; Filser, J.; Miao, A.J.; Quigg, A.; Santschi, P.H.; Sigg, L. Environmental Behavior and Ecotoxicity of Engineered Nanoparticles to Algae, Plants, and Fungi. *Ecotoxicology* **2008**, *17*, <https://link.springer.com/article/10.1007/s10646-008-0214-0>.
77. Kaur, A.; Preet, S.; Kumar, V.; Kumar, R.; Kumar, R. Synergetic Effect of Vancomycin Loaded Silver Nanoparticles for Enhanced Antibacterial Activity. *Colloids Surfaces B Biointerfaces* **2019**, *176*, <https://doi.org/10.1016/j.colsurfb.2018.12.043>.
78. Fu, P.P.; Xia, Q.; Hwang, H.M.; Ray, P.C.; Yu, H. Mechanisms of Nanotoxicity: Generation of Reactive Oxygen Species. *J. Food Drug Anal.* **2014**, *22*, 64–75, <https://doi.org/10.1016/j.jfda.2014.01.005>.
79. He, X.; Aker, W.G.; Fu, P.P.; Hwang, H.M. Toxicity of Engineered Metal Oxide Nanomaterials Mediated by Nano-Bio-Eco-Interactions: A Review and Perspective. *Environ. Sci. Nano* **2015**, *2*, <https://pubs.rsc.org/en/content/articlelanding/2015/en/c5en00094g>.
80. Dayem, A.A.; Hossain, M.K.; Lee, S. Bin; Kim, K.; Saha, S.K.; Yang, G.M.; Choi, H.Y.; Cho, S.G. The Role of Reactive Oxygen Species (ROS) in the Biological Activities of Metallic Nanoparticles. *Int. J. Mol. Sci.* **2017**, *18*, <https://doi.org/10.3390/ijms18010120>.
81. Snezhkina, A. V.; Kudryavtseva, A. V.; Kardymon, O.L.; Savvateeva, M. V.; Melnikova, N. V.; Krasnov, G.S.; Dmitriev, A.A. ROS Generation and Antioxidant Defense Systems in Normal and Malignant Cells. *Oxid. Med. Cell. Longev.* **2020**, *2019*, <https://doi.org/10.1155/2019/6175804>.
82. Halliwell, B. Reactive Species and Antioxidants. Redox Biology Is a Fundamental Theme of Aerobic Life. *Plant Physiol.* **2006**, *141*, 312-322, <https://doi.org/10.1104/pp.106.077073>.
83. Paravicini, T.M.; Touyz, R.M. NADPH Oxidases, Reactive Oxygen Species, and Hypertension: Clinical Implications and Therapeutic Possibilities. *Diabetes Care* **2008**, *31 Suppl 2*, S170-S180, <https://doi.org/10.2337/dc08-s247>.
84. Yin, H.; Xu, L.; Porter, N.A. Free Radical Lipid Peroxidation: Mechanisms and Analysis. *Chem. Rev.* **2011**, *111*, 5944-5972, <https://doi.org/10.1021/cr200084z>.
85. Kowaltowski, A.J.; Vercesi, A.E. Mitochondrial Damage Induced by Conditions of Oxidative Stress. *Free Radic. Biol. Med.* **1999**, *26*, [https://doi.org/10.1016/S0891-5849\(98\)00216-0](https://doi.org/10.1016/S0891-5849(98)00216-0).

86. Xie, H.; Mason, M.M.; Wise, J.P. Genotoxicity of Metal Nanoparticles. *Rev. Environ. Health* **2011**, *26*, <https://doi.org/10.1515/REVEH.2011.033>.
87. Wu, H.; Yin, J.J.; Wamer, W.G.; Zeng, M.; Lo, Y.M. Reactive Oxygen Species-Related Activities of Nano-Iron Metal and Nano-Iron Oxides. *J. Food Drug Anal.* **2014**, *22*, 86-94, <https://doi.org/10.1016/j.jfda.2014.01.007>.
88. Huang, Z.; Zheng, X.; Yan, D.; Yin, G.; Liao, X.; Kang, Y.; Yao, Y.; Huang, D.; Hao, B. Toxicological Effect of ZnO Nanoparticles Based on Bacteria. *Langmuir* **2008**, *24*, <https://doi.org/10.1021/la7035949>.
89. Dizaj, S.M.; Lotfipour, F.; Barzegar-Jalali, M.; Zarrintan, M.H.; Adibkia, K. Antimicrobial Activity of the Metals and Metal Oxide Nanoparticles. *Mater. Sci. Eng. C* **2014**, *44*, 278-284, <https://doi.org/10.1016/j.msec.2014.08.031>.
90. Azam, A.; Ahmed, A.S.; Oves, M.; Khan, M.S.; Habib, S.S.; Memic, A. Antimicrobial Activity of Metal Oxide Nanoparticles against Gram-Positive and Gram-Negative Bacteria: A Comparative Study. *Int. J. Nanomedicine* **2012**, *7*, <https://doi.org/10.2147/IJN.S35347>.
91. Li, Y.; Zhang, W.; Niu, J.; Chen, Y. Mechanism of Photogenerated Reactive Oxygen Species and Correlation with the Antibacterial Properties of Engineered Metal-Oxide Nanoparticles. *ACS Nano* **2012**, *6*, <https://doi.org/10.1021/nn300934k>.
92. Canaparo, R.; Foglietta, F.; Limongi, T.; Serpe, L. Biomedical Applications of Reactive Oxygen Species Generation by Metal Nanoparticles. *Materials (Basel)*. **2021**, *14*, <https://doi.org/10.3390/ma14010053>.
93. Jafari, S.; Mahyad, B.; Hashemzadeh, H.; Janfaza, S.; Gholikhani, T.; Tayebi, L. Biomedical Applications of TiO₂ Nanostructures: Recent Advances. *Int. J. Nanomedicine* **2020**, *15*, <https://doi.org/10.2147/ijn.s249441>.
94. Castellano, J.J.; Shafii, S.M.; Ko, F.; Donate, G.; Wright, T.E.; Mannari, R.J.; Payne, W.G.; Smith, D.J.; Robson, M.C. Comparative Evaluation of Silver-Containing Antimicrobial Dressings and Drugs. *Int. Wound J.* **2007**, *4*, <https://doi.org/10.1111/j.1742-481X.2007.00316.x>.
95. Polívková, M.; Štrublová, V.; Hubáček, T.; Rimpelová, S.; Švorčík, V.; Siegel, J. Surface Characterization and Antibacterial Response of Silver Nanowire Arrays Supported on Laser-Treated Polyethylene Naphthalate. *Mater. Sci. Eng. C* **2017**, *72*, <https://doi.org/10.1016/j.msec.2016.11.072>.
96. Yu, J.; Zhang, W.; Li, Y.; Wang, G.; Yang, L.; Jin, J.; Chen, Q.; Huang, M. Synthesis, Characterization, Antimicrobial Activity and Mechanism of a Novel Hydroxyapatite Whisker/Nano Zinc Oxide Biomaterial. *Biomed. Mater.* **2015**, *10*, <https://doi.org/10.1088/1748-6041/10/1/015001>.
97. Zhang, H.; Lv, X.; Li, Y.; Wang, Y.; Li, J. P25-Graphene Composite as a High Performance Photocatalyst. *ACS Nano* **2010**, *4*, <https://doi.org/10.1021/nn901221k>.
98. Sim, W.; Barnard, R.T.; Blaskovich, M.A.T.; Ziora, Z.M. Antimicrobial Silver in Medicinal and Consumer Applications: A Patent Review of the Past Decade (2007–2017). *Antibiotics* **2018**, *7*, <https://doi.org/10.3390/antibiotics7040093>.
99. Gurunathan, S.; Han, J.W.; Kwon, D.N.; Kim, J.H. Enhanced Antibacterial and Anti-Biofilm Activities of Silver Nanoparticles against Gram-Negative and Gram-Positive Bacteria. *Nanoscale Res. Lett.* **2014**, *9*, <https://doi.org/10.1186/1556-276X-9-373>.
100. Bharti, S.; Mukherji, S.; Mukherji, S. Enhanced Antibacterial Activity of Decahedral Silver Nanoparticles. *J. Nanoparticle Res.* **2020**, *23*, <https://doi.org/10.1007/s11051-020-05106-z>.
101. Panáček, A.; Kvítek, L.; Prucek, R.; Kolář, M.; Večeřová, R.; Pizúrová, N.; Sharma, V.K.; Nevěčná, T.; Zbořil, R. Silver Colloid Nanoparticles: Synthesis, Characterization, and Their Antibacterial Activity. *J. Phys. Chem. B* **2006**, *110*, <https://doi.org/10.1021/jp063826h>.
102. Qais, F.A.; Shafiq, A.; Khan, H.M.; Husain, F.M.; Khan, R.A.; Alenazi, B.; Alsalmeh, A.; Ahmad, I. Antibacterial Effect of Silver Nanoparticles Synthesized Using *Murraya Koenigii* (L.) against Multidrug-Resistant Pathogens. *Bioinorg. Chem. Appl.* **2019**, *2019*, <https://doi.org/10.1155/2019/4649506>.
103. Lara, H.H.; Ayala-Núñez, N. V.; del Turrent, L.C.I.; Padilla, C.R. Bactericidal Effect of Silver Nanoparticles against Multidrug-Resistant Bacteria. *World J. Microbiol. Biotechnol.* **2010**, *26*, <https://doi.org/10.1007/s11274-009-0211-3>.
104. Franci, G.; Falanga, A.; Galdiero, S.; Palomba, L.; Rai, M.; Morelli, G.; Galdiero, M. Silver Nanoparticles as Potential Antibacterial Agents. *Molecules* **2015**, *20*, <https://doi.org/10.3390/molecules20058856>.
105. Pal, S.; Tak, Y.K.; Song, J.M. Does the Antibacterial Activity of Silver Nanoparticles Depend on the Shape of the Nanoparticle? A Study of the Gram-Negative Bacterium *Escherichia Coli*. *Appl. Environ. Microbiol.* **2007**, *73*, <https://doi.org/10.1128/AEM.02218-06>.
106. Deshmukh, S.P.; Patil, S.M.; Mullani, S.B.; Delekar, S.D. Silver Nanoparticles as an Effective Disinfectant: A Review. *Mater. Sci. Eng. C* **2019**, *97*, <https://doi.org/10.1016/j.msec.2018.12.102>.
107. Pillai, A.M.; Sivasankarapillai, V.S.; Rahdar, A.; Joseph, J.; Sadeghfar, F.; Anuf A, R.; Rajesh, K.; Kyzas, G.Z. Green Synthesis and Characterization of Zinc Oxide Nanoparticles with Antibacterial and Antifungal Activity. *J. Mol. Struct.* **2020**, *1211*, <https://doi.org/10.1016/j.molstruc.2020.128107>.
108. Aldosari, M.A.; Darwish, S.S.; Adam, M.A.; Elmarzughi, N.A.; Ahmed, S.M. Using ZnO Nanoparticles in Fungal Inhibition and Self-Protection of Exposed Marble Columns in Historic Sites. *Archaeol. Anthropol. Sci.* **2019**, *11*, <https://doi.org/10.1007/s12520-018-0762-z>.
109. Kasemets, K.; Ivask, A.; Dubourguier, H.C.; Kahru, A. Toxicity of Nanoparticles of ZnO, CuO and TiO₂ to

- Yeast *Saccharomyces Cerevisiae*. *Toxicol. Vitro*. **2009**, *23*, <https://doi.org/10.1016/j.tiv.2009.05.015>.
110. Brunner, T.J.; Wick, P.; Manser, P.; Spohn, P.; Grass, R.N.; Limbach, L.K.; Bruinink, A.; Stark, W.J. *In vitro* Cytotoxicity of Oxide Nanoparticles: Comparison to Asbestos, Silica, and the Effect of Particle Solubility. *Environ. Sci. Technol.* **2006**, *40*, <https://doi.org/10.1021/es052069i>.
111. Li, M.; Zhu, L.; Lin, D. Toxicity of ZnO Nanoparticles to *Escherichia Coli*: Mechanism and the Influence of Medium Components. *Environ. Sci. Technol.* **2011**, *45*, <https://doi.org/10.1021/es102624t>.
112. Lipovsky, A.; Nitzan, Y.; Gedanken, A.; Lubart, R. Antifungal Activity of ZnO Nanoparticles—the Role of ROS Mediated Cell Injury. *Nanotechnology* **2011**, *22*, <https://doi.org/10.1088/0957-4484/22/10/105101>.
113. Sawai, J.; Shoji, S.; Igarashi, H.; Hashimoto, A.; Kokugan, T.; Shimizu, M.; Kojima, H. Hydrogen Peroxide as an Antibacterial Factor in Zinc Oxide Powder Slurry. *J. Ferment. Bioeng.* **1998**, *86*, [https://doi.org/10.1016/S0922-338X\(98\)80165-7](https://doi.org/10.1016/S0922-338X(98)80165-7).
114. Sirelkhatim, A.; Mahmud, S.; Seeni, A.; Kaus, N.H.M.; Ann, L.C.; Bakhori, S.K.M.; Hasan, H.; Mohamad, D. Review on Zinc Oxide Nanoparticles: Antibacterial Activity and Toxicity Mechanism. *Nano-Micro Lett.* **2015**, *7*, <https://doi.org/10.1007/s40820-015-0040-x>.
115. Allahverdiyev, A.M.; Abamor, E.S.; Bagirova, M.; Rafailovich, M. Antimicrobial Effects of TiO₂ and Ag₂O Nanoparticles against Drug-Resistant Bacteria and Leishmania Parasites. *Future Microbiol.* **2011**, *6*, 933–940, <https://doi.org/10.2217/FMB.11.78>.
116. Khashan, K.S.; Sulaiman, G.M.; Abdulameer, F.A.; Albukhaty, S.; Ibrahim, M.A.; Al-Muhimeed, T.; Alobaid, A.A. Antibacterial Activity of TiO₂ Nanoparticles Prepared by One-Step Laser Ablation in Liquid. *Appl. Sci.* **2021**, *11*, <https://doi.org/10.3390/app11104623>.
117. Tsuang, Y.H.; Sun, J.S.; Huang, Y.C.; Lu, C.H.; Chang, W.H.S.; Wang, C.C. Studies of Photokilling of Bacteria Using Titanium Dioxide Nanoparticles. *Artif. Organs* **2008**, *32*, <https://doi.org/10.1111/j.1525-1594.2007.00530.x>.
118. Li, Y.F.; Liu, Z.P.; Liu, L.; Gao, W. Mechanism and Activity of Photocatalytic Oxygen Evolution on Titania Anatase in Aqueous Surroundings. *J. Am. Chem. Soc.* **2010**, *132*, <https://doi.org/10.1021/ja105340b>.
119. Wong, M.S.; Chu, W.C.; Sun, D.S.; Huang, H.S.; Chen, J.H.; Tsai, P.J.; Lin, N.T.; Yu, M.S.; Hsu, S.F.; Wang, S.L.; *et al.* Visible-Light-Induced Bactericidal Activity of a Nitrogen-Doped Titanium Photocatalyst against Human Pathogens. *Appl. Environ. Microbiol.* **2006**, *72*, <https://doi.org/10.1128/AEM.02580-05>.
120. Qais, F.A.; Khan, M.S.; Ahmad, I. Nanoparticles as Quorum Sensing Inhibitor: Prospects and Limitations. *Biotechnol. Appl. Quor. Sens. Inhib.* **2018**, 227–244, https://doi.org/10.1007/978-981-10-9026-4_11.
121. Qais, F.A.; Shafiq, A.; Ahmad, I.; Husain, F.M.; Khan, R.A.; Hassan, I. Green Synthesis of Silver Nanoparticles Using *Carum Copticum*: Assessment of Its Quorum Sensing and Biofilm Inhibitory Potential against Gram Negative Bacterial Pathogens. *Microb. Pathog.* **2020**, *144*, <https://doi.org/10.1016/j.micpath.2020.104172>.
122. Czárán, T.; Hoekstra, R.F. A Spatial Model of the Evolution of Quorum Sensing Regulating Bacteriocin Production. *Behav. Ecol.* **2007**, *18*, <https://doi.org/10.1093/beheco/arm061>.
123. Ozdal, M.; Gurkok, S. Recent Advances in Nanoparticles as Antibacterial Agent. *ADMET DMPK* **2022**, *10*, <https://doi.org/10.5599/admet.1172>.
124. Hayat, S.; Muzammil, S.; Shabana; Aslam, B.; Siddique, M.H.; Saqalein, M.; Nisar, M.A. Quorum Quenching: Role of Nanoparticles as Signal Jammers in Gram-Negative Bacteria. *Future Microbiol.* **2019**, *14*, <https://doi.org/10.2217/fmb-2018-0257>.
125. Sadekuzzaman, M.; Yang, S.; Mizan, M.F.R.; Ha, S.D. Current and Recent Advanced Strategies for Combating Biofilms. *Compr. Rev. Food Sci. Food Saf.* **2015**, *14*, <https://doi.org/10.1111/1541-4337.12144>.
126. Ali, S.G.; Ansari, M.A.; Sajid Jamal, Q.M.; Khan, H.M.; Jalal, M.; Ahmad, H.; Mahdi, A.A. Antiquorum Sensing Activity of Silver Nanoparticles in *P. Aeruginosa*: An *in silico* Study. *Silico Pharmacol.* **2017**, *5*, <https://doi.org/10.1007/s40203-017-0031-3>.
127. Saleh, M.M.; Sadeq, R.A.; Abdel Latif, H.K.; Abbas, H.A.; Askoura, M. Zinc Oxide Nanoparticles Inhibits Quorum Sensing and Virulence in *Pseudomonas Aeruginosa*. *Afr. Health Sci.* **2019**, *19*, <https://doi.org/10.4314/ahs.v19i2.28>.
128. Singh, B.R.; Singh, B.N.; Singh, A.; Khan, W.; Naqvi, A.H.; Singh, H.B. Mycofabricated Biosilver Nanoparticles Interrupt *Pseudomonas Aeruginosa* Quorum Sensing Systems. *Sci. Rep.* **2015**, *5*, <https://doi.org/10.1038/srep13719>.
129. Garc Ia-Lara, B.; Saucedo-Mora, M.A.; Rold An-S Anchez, J.A.; P Erez-Eretza, B.; Ramasamy, M.; Lee, J.; Coria-Jimenez, R.; Tapia, M.; Varela-Guerrero, V.; Garc Ia-Contreras, R. Inhibition of Quorum-sensing-dependent Virulence Factors and Biofilm Formation of Clinical and Environmental *Pseudomonas Aeruginosa* Strains by ZnO Nanoparticles. *Wiley Online Libr.* **2015**, *61*, 299–305, <https://doi.org/10.1111/lam.12456>.
130. Hussain, A.; Alajmi, M.F.; Khan, M.A.; Pervez, S.A.; Ahmed, F.; Amir, S.; Husain, F.M.; Khan, M.S.; Shaik, G.M.; Hassan, I.; *et al.* Biosynthesized Silver Nanoparticle (AgNP) from Pandanus Odorifer Leaf Extract Exhibits Anti-Metastasis and Anti-Biofilm Potentials. *Front. Microbiol.* **2019**, *10*, <https://doi.org/10.3389/fmicb.2019.00008>.
131. Ali, S.G.; Ansari, M.A.; Khan, H.M.; Jalal, M.; Mahdi, A.A.; Cameotra, S.S. Crataeva Nurvala Nanoparticles Inhibit Virulence Factors and Biofilm Formation in Clinical Isolates of *Pseudomonas*

- Aeruginosa. *J. Basic Microbiol.* **2017**, *57*, 193–203, <https://doi.org/10.1002/JOBM.201600175>.
132. Masurkar, S.A.; Chaudhari, P.R.; Shidore, V.B.; Kamble, S.P. Effect of Biologically Synthesised Silver Nanoparticles on Staphylococcus Aureus Biofilm Quenching and Prevention of Biofilm Formation. *IET Nanobiotechnology* **2012**, *6*, <https://doi.org/10.1049/iet-nbt.2011.0061>.
133. Srinivasan, R.; Vigneshwari, L.; Rajavel, T.; Durgadevi, R.; Kannappan, A.; Balamurugan, K.; Pandima Devi, K.; Veera Ravi, A. Biogenic Synthesis of Silver Nanoparticles Using Piper Betle Aqueous Extract and Evaluation of Its Anti-Quorum Sensing and Antibiofilm Potential against Uropathogens with Cytotoxic Effects: An *in vitro* and *in vivo* Approach. *Environ. Sci. Pollut. Res.* **2018**, *25*, <https://doi.org/10.1007/s11356-017-1049-0>.
134. Ali, S.G.; Ansari, M.A.; Jamal, Q.M.S.; Almatroudi, A.; Alzohairy, M.A.; Alomary, M.N.; Rehman, S.; Mahadevamurthy, M.; Jalal, M.; Khan, H.M.; *et al.* Butea Monosperma Seed Extract Mediated Biosynthesis of ZnO NPs and Their Antibacterial, Antibiofilm and Anti-Quorum Sensing Potentialities. *Arab. J. Chem.* **2021**, *14*, <https://doi.org/10.1016/j.arabjc.2021.103044>.
135. Al-Shabib, N.A.; Husain, F.M.; Ahmed, F.; Khan, R.A.; Ahmad, I.; Alsharaeh, E.; Khan, M.S.; Hussain, A.; Rehman, M.T.; Yusuf, M.; *et al.* Biogenic Synthesis of Zinc Oxide Nanostructures from Nigella Sativa Seed: Prospective Role as Food Packaging Material Inhibiting Broad-Spectrum Quorum Sensing and Biofilm. *Sci. Rep.* **2016**, *6*, <https://doi.org/10.1038/srep36761>.
136. Lee, J.H.; Kim, Y.G.; Cho, M.H.; Lee, J. ZnO Nanoparticles Inhibit Pseudomonas Aeruginosa Biofilm Formation and Virulence Factor Production. *Microbiol. Res.* **2014**, *169*, <https://doi.org/10.1016/j.micres.2014.05.005>.
137. Kamli, M.R.; Malik, M.A.; Srivastava, V.; Sabir, J.S.M.; Mattar, E.H.; Ahmad, A. Biogenic ZnO Nanoparticles Synthesized from Origanum Vulgare Abrogates Quorum Sensing and Biofilm Formation in Opportunistic Pathogen Chromobacterium Violaceum. *Pharmaceutics* **2021**, *13*, <https://doi.org/10.3390/pharmaceutics13111743>.
138. Ahmed, F.Y.; Aly, U.F.; Abd El-Baky, R.M.; Waly, N.G.F.M. Effect of Titanium Dioxide Nanoparticles on the Expression of Efflux Pump and Quorum-Sensing Genes in Mdr Pseudomonas Aeruginosa Isolates. *Antibiotics* **2021**, *10*, <https://doi.org/10.3390/antibiotics10060625>.
139. CaNanoLab. Available online: <https://cananolab.cancer.gov/#/> (accessed on 28 September 2021).
140. ENanoMapper. Available online: <https://data.enanomapper.net/> (accessed on 28 September 2021).
141. Nanomaterial Registry Available online: <https://nanomaterialregistry.net/> (accessed on 28 September 2021).
142. Nanoparticle Information Library Available online: <http://nanoparticlelibrary.net/> (accessed on 28 September 2021).
143. PubVINAS. Available online: <http://www.pubvinas.com/> (accessed on 28 September 2021).
144. Morris, S. A., Gaheen, S., Lijowski, M., Heiskanen, M., Klemm, J. Experiences in Supporting the Structured Collection of Cancer Nanotechnology Data Using CaNanoLab. *beilstein-journals.org.* 2015, *6*, 1580-1593, <https://doi.org/10.3762/bjnano.6.161>.
145. Ji, Z.; Guo, W.; Sakkiah, S.; Liu, J.; Patterson, T.A.; Hong, H. Nanomaterial Databases: Data Sources for Promoting Design and Risk Assessment of Nanomaterials. *Nanomaterials* **2021**, *11*, 1599, <https://doi.org/10.3390/nano11061599>.
146. Tropsha, A.; Mills, K.C.; Hickey, A.J. Reproducibility, Sharing and Progress in Nanomaterial Databases. *Nat. Nanotechnol.* **2017**, *12*, 1111-1114, <https://doi.org/10.1038/nnano.2017.233>.
147. Yan, X.; Sedykh, A.; Wang, W.; Yan, B.; Zhu, H. Construction of a Web-Based Nanomaterial Database by Big Data Curation and Modeling Friendly Nanostructure Annotations. *Nat. Commun.* **2020**, *11*, <https://doi.org/10.1038/s41467-020-16413-3>.